

Material No.: Code:
1.2550 60WCrV8

DE - Brand:
Hidalgo I

Chemical composition:
 (Typical analysis in %)

C	W	Cr	V				
0,60	2,00	1,00	0,15				

Steel properties:

Cold work steel with very good toughness, dimensionally stable, impact resistant, high hardening capacity. Similar to AISI S1.

Applications:

Cold shear knives, paper and wood cutting knives, cutting tools for plates up to 10 mm, ejector pins, air hammers.

Condition of delivery:

Soft annealed to max. 229 HB


Physical properties:

Thermal expansion coefficient	$\left[\frac{10^{-6} \cdot \text{m}}{\text{m} \cdot \text{K}} \right]$	20-100°C	20-200°C	20-300°C	20-400°C
		10,9	11,5	12,0	12,4
Thermal conductivity	$\left[\frac{\text{W}}{\text{m} \cdot \text{K}} \right]$	20°C	350°C		
		31,9	29,6		


Heat treatment:

Soft annealing	Temperature	Cooling	Hardness
	720 - 760°C	furnace	max. 229 HB
Stress relief annealing	Temperature	Cooling	
	600 - 650°C	furnace	
Hardening	Temperature	Cooling	Tempering
	860 - 900°C	oil or hot bath 180 - 220°C	see tempering diagram


(1.2550) Thermal Cycle Diagram

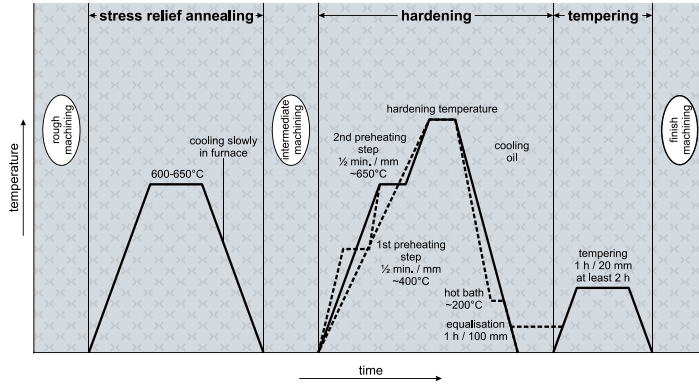

Continuous Cooling Transformation Diagram (CCT)

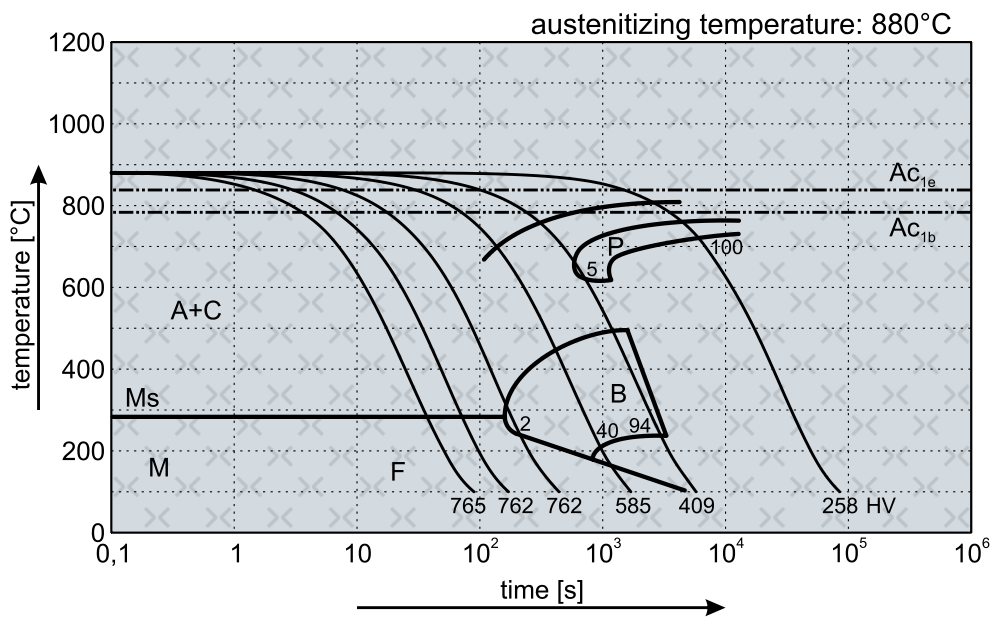

Tempering Diagram

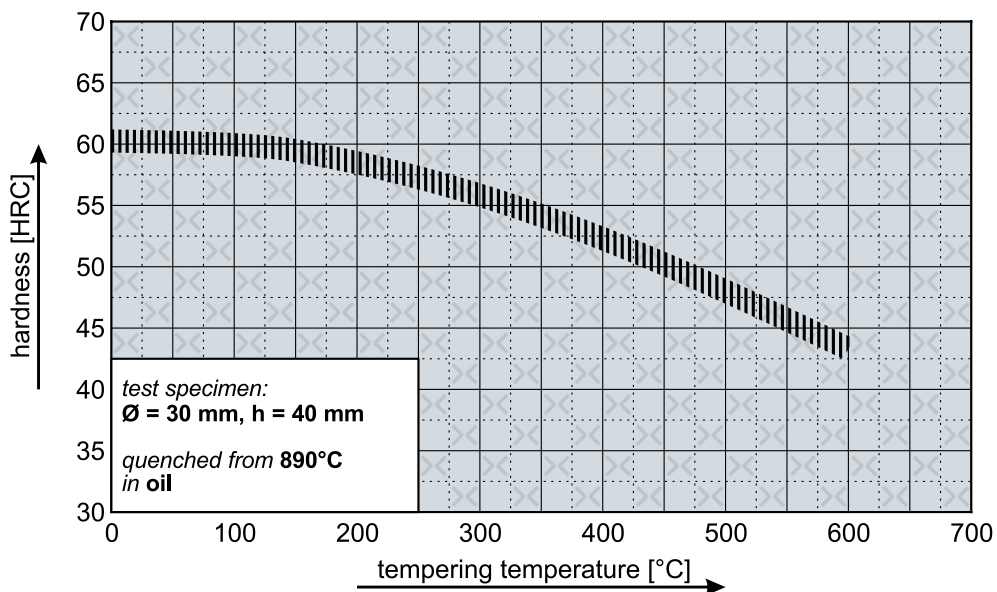

Remarks: All technical information is for reference only.